

REPORT DOCUMENTATION PAGE

AFRL-SR-BL-TR-00-

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comm collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Dire Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reductio

0227

1. AGENCY USE ONLY (Leave Blank)		2. REPORT DATE 01 Sep 98		3. REPORT TYPE AND DATES COVERED Final Report # 1; 01 Dec 97 - 30 Nov 98 30 Nov 99	
4. TITLE AND SUBTITLE Novel Epitaxial Growth Technologies for Long-Wavelength (1.1-1.5 micron) Vertical-Cavity Surface-Emitting Lasers and Optical Switches for High-Performance Optical Information Networks				5. FUNDING NUMBERS F49620-98-1-0129	
6. AUTHORS Julian Cheng					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) The University of New Mexico Center for High Technology Materials 1313 Goddard S.E. Albuquerque, NM 87106				8. PERFORMING ORGANIZATION REPORT NUMBER PR-1	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Office of Scientific Research Ballston Tower II 801 N. Randolph St., Room 732 Arlington, VA 22203-1977				10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES					
12a. DISTRIBUTION / AVAILABILITY STATEMENT Unlimited				12b. DISTRIBUTION CODE UNL	
13. ABSTRACT (Maximum 200 words) The goal of this research program is to develop novel techniques for the epitaxial growth and fabrication of vertical-cavity surface-emitting laser structures with lasing wavelengths in the 1.1-1.5 micron regime. Special emphasis will be on the realization of 1300 nm VCSELs and monolithic VCSEL arrays that are useful for the parallel optical data links that will interconnect future computer networks, whose nodes may be distributed across a wide range of distances and are interconnected by optical fibers. The 1300nm VCSELs will provide improved fiber transmission performance as well as a more unified technology platform for the different levels of the interconnection heirarchy. One goal is to design and demonstrate a practical 1300nm VCSEL structure that can be grown by a single epitaxial growth on a convention, high quality GaAs substrate. These structures will use InGaAsN quantum wells, as well as GaAs/AIAs distributed Bragg reflector (DBR) mirrors with a large index difference, which reduces the total thickness to a tract-able level that makes a single-growth approach possible. In this program, we will develop an optimum device design for the fabrication of these VCSEL structures, and we will integrate them into monolithic arrays. We will evaluate the performance of the VCSELs in parallel optical links as well as in VCSEL-based optical switching networks.					
14. SUBJECT TERMS VCSELs, monolithic arrays, optical interconnects				15. NUMBER OF PAGES 7 incll this page	
				16. PRICE CODE NSP	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UNL		

NSN 7540-01-280-5500

Standard Form 298 (Rev. 2-89)
Prescribed by ANSI Std. Z39-1
298-102

DTIC QUALITY INSPECTED 4

1. Statement of Work (SOW):

The goal of this two-year research program is to develop a novel technology for the epitaxial growth and fabrication of vertical-cavity surface-emitting laser structures with lasing wavelengths in the 1.1 μm to 1.5 μm regime. Special emphasis will be on the realization of 1300 nm VCSELs and monolithic VCSEL arrays, which are useful for the parallel optical data links that will interconnect future computer networks, whose nodes may be distributed across a wide range of distances and are interconnected by optical fibers. The use 1300 nm VCSELs will provide improved fiber transmission performance as well as a more unified technology platform for the different levels of the interconnection hierarchy. We will design and demonstrate a practical 1300 nm VCSEL structure that can be grown by conventional growth techniques on a ternary InGaAs substrate. These structures will contain a GRINSCH active region with one or more strain-compensated InGaAs quantum wells, as well as InGaAs/InAlAs distributed Bragg reflector (DBR) mirrors with a large index difference, which allows the total thickness of each mirror to be reduced, thus making the growth of the complete VCSEL tractable. We will develop an optimum device design for the fabrication of these VCSEL structures, and we will integrate them into monolithic arrays. We will evaluate the performance of these VCSELs in parallel optical links as well as in VCSEL-based optical switching networks. The lasing wavelengths of each array will also be graded using specialized growth techniques that will be developed, which will have important potential applications in wavelength-multiplexed or wavelength-switched optical information networks.

2. Research Program Summary:

The goal of this two-year research program is to develop novel technologies for the epitaxial growth and fabrication of vertical-cavity surface-emitting laser structures with lasing wavelengths in the 1.1 μm to 1.5 μm regime. Special emphasis will be on the realization of 1300 nm VCSELs and monolithic VCSEL arrays that are useful for the parallel optical data links that will interconnect future computer networks, whose nodes may be distributed across a wide range of distances and are interconnected by optical fibers. The use 1300 nm VCSELs will provide improved fiber transmission performance as well as a more unified technology platform for the different levels of the interconnection hierarchy. One goal is to design and demonstrate a practical 1300 nm VCSEL structure that can be grown by a single epitaxial growth on a conventional, high quality GaAs substrate. These structures will use InGaAsN quantum wells, as well as GaAs/AlAs distributed Bragg reflector (DBR) mirrors with a large index difference, which reduces the total thickness to a tractable level that makes a single-growth approach possible. In this program, we will develop an optimum device design for the fabrication of these VCSEL structures, and we will integrate them into monolithic arrays. We will evaluate the performance of these VCSELs in parallel optical links as well as in VCSEL-based optical switching networks.

3. Epitaxial Approach:

VCSELs that emit at longer wavelengths have also been demonstrated using highly-complex, multiple-growth technologies, such as wafer-fusion (1.3 and 1.5 μm VCSELs), or the use of compliant substrates, whose manufacturability and reliability

remain in doubt. A single-growth approach would be the ideal solution to the long-wavelength VCSEL problem. *At present, there is no all-epitaxially-grown long wavelength VCSEL technology*, nor is there any other approach with proven performance or reliability. Long-wavelength operation using a single-growth epitaxial VCSEL structure grown on a GaAs substrate has not yet been demonstrated due to the inherent problem of a large lattice mismatch ($\epsilon > 2.5\%$) between the $\text{In}_x\text{Ga}_{1-x}\text{As}$ ($x > 0.4$) active layer and the GaAs substrate. The growth of a highly-strained VCSEL structure on a ternary substrate represents a promising single-growth approach, but the broad availability of these substrates in the future is unknown. To solve this problem, we propose a new single-growth epitaxial approach that requires only conventional GaAs substrates and uses only conventional GaAs VCSEL processing technology.

This new approach uses a novel narrow-bandgap material, InGaAsN, lattice-matched to GaAs - as the active region, while preserving the larger index difference of the conventional AlGaAs/AlAs DBRs. It offers a structural simplicity that makes VCSELs far easier to fabricate than approaches that require the wafer bonding of one or more GaAs/AlGaAs DBRs to an InGaAsP/InP active region. The objective of this research is to investigate the use of such a strain-free material family, $\text{In}_x\text{Ga}_{1-x}\text{As}_{1-y}\text{N}_y$, to achieve $1.3\ \mu\text{m}$ VCSEL operation on a GaAs substrate. We will develop a practical and potentially manufacturable new VCSEL technology that is based on a single-growth using conventional growth systems, using only conventional substrates and established device fabrication techniques.

4. Long Wavelength $1.3\ \mu\text{m}$ VCSELs using $\text{In}_x\text{Ga}_{1-x}\text{As}_{1-y}\text{N}_y$ active layers grown on GaAs Substrates

Fig. 1 shows the bandgap energy as a function of lattice constant for a variety of III-V compound semiconductor materials. Due to the large electronegativity of nitrogen atoms, a negative bandgap energy has been predicted for N-containing compounds such as $\text{GaAs}_{1-x}\text{N}_x$, $\text{GaP}_{1-x}\text{N}_x$, and $\text{AlAs}_{1-x}\text{N}_x$. This huge bowing of bandgap energy provides another degree of freedom in bandgap engineering by providing novel material systems that can be exploited to realize long-wavelength lasers or other electronic devices on GaAs substrates. For example, adding 10% In to GaAs increases the lattice constant of the $\text{In}_{0.1}\text{Ga}_{0.9}\text{As}$ layer, placing it under compressive strain, while adding approximately 2% N to the $\text{In}_{0.1}\text{Ga}_{0.9}\text{As}$ layer decreases its lattice constant and thus compensates for the compressive strain. Thus a strain-free material, $\text{In}_x\text{Ga}_{1-x}\text{As}_{1-y}\text{N}_y$ grown on GaAs, can be easily obtained by choosing suitable compositions x and y . Furthermore, due to this unique bandgap bowing effect, the bandgap energy of $\text{In}_x\text{Ga}_{1-x}\text{As}_{1-y}\text{N}_y$ can be significantly reduced below that of GaAs. This result strongly suggests that the $\text{In}_x\text{Ga}_{1-x}\text{As}_{1-y}\text{N}_y$ alloy has a great potential for long-wavelength laser applications.

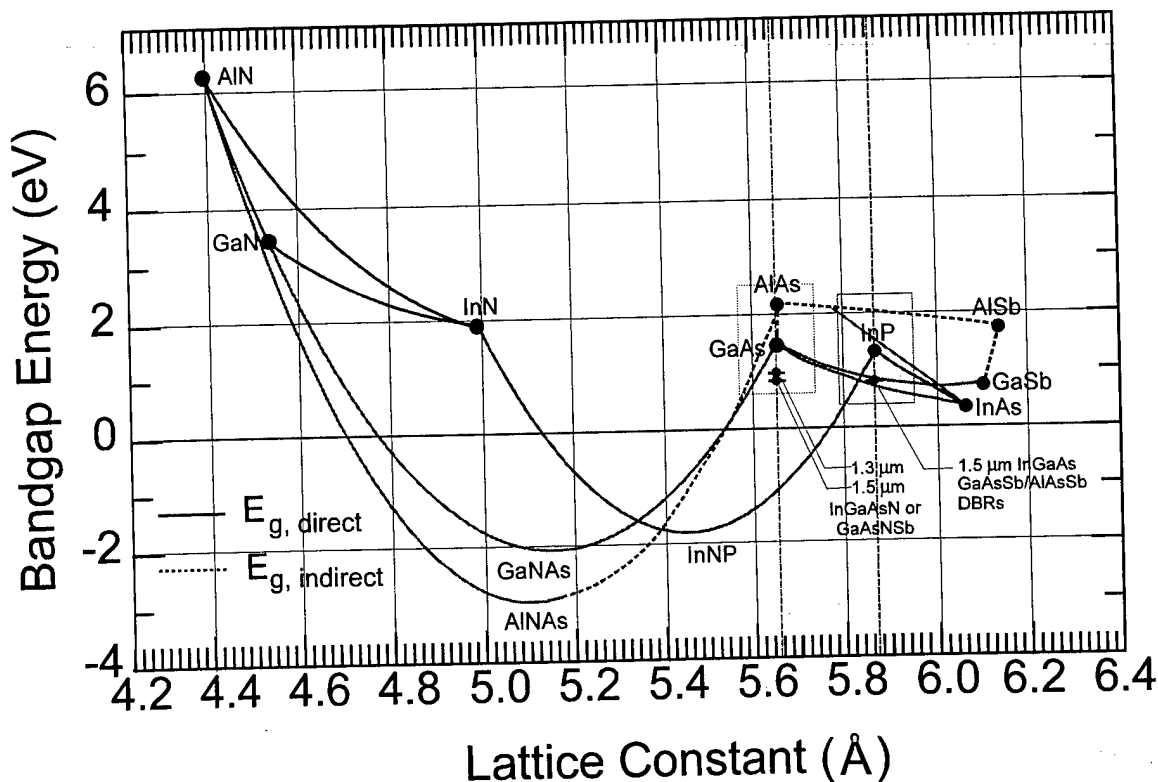


Fig. 1 The composition dependence of the bandgap energies of III-NAs and III-NP alloys calculated based on the Van Vechten model. The boxes indicate two different material systems that can be used to achieve long wavelength VCSELs.

5. Pulsed Lasing of Multi-Quantum Well GaInNAs/GaAs Lasers with Low Threshold Current Density Grown by MOCVD

The $\text{Ga}_{1-x}\text{In}_x\text{N}_y\text{As}_{1-y}/\text{GaAs}$ material system represents a promising approach for achieving long wavelength semiconductor lasers with a large characteristics temperature (T_0) as well as VCSELs on a high-quality GaAs substrate. For VCSELs, this epitaxial approach takes advantage of the large index difference of GaAs/AlAs DBR mirrors (thus smaller growth thickness), as well as the established processing technology of AlGaAs/GaAs VCSELs. Pulsed lasing of edge-emitting $\text{Ga}_{1-x}\text{In}_x\text{N}_y\text{As}_{1-y}/\text{GaAs}$ quantum well (QW) lasers has previously been achieved at $1.18 \mu\text{m}$ and at $1.31 \mu\text{m}$ at room temperature using material grown by gas source MBE [1], with a threshold current as low as 1.4 kA/cm^2 . However, the progress in MOCVD-grown GaInNAs/GaAs material has lagged behind, and the best result to date was achieved by a 2-QW laser under pulsed lasing conditions [2], with a lasing wavelength of $\sim 1.18 \mu\text{m}$ and a threshold current density of 3.37 kA/cm^2 . This paper reports a significant improvement in the performance of MOCVD-grown $\text{Ga}_{1-x}\text{In}_x\text{N}_y\text{As}_{1-y}/\text{GaAs}$ lasers. Using a new MOCVD regrowth technique [3], 3-QW $\text{Ga}_{1-x}\text{In}_x\text{N}_y\text{As}_{1-y}/\text{GaAs}$ edge-emitting lasers with $x=0.3$ and $y \sim 0.3-0.4$ % have been achieved, with lasing wavelengths in the $1.15-1.19 \mu\text{m}$ regime and threshold current density as low as $\sim 600-700 \text{ A/cm}^2$, which is the lowest for any MOCVD-grown devices. Ridge-waveguide lasers as well as planar broad stripe lasers defined by the selective lateral wet oxidation of an $\text{Al}_{0.98}\text{Ga}_{0.02}\text{As}$ layer have been fabricated.

The GaInNAs lasers were grown in an IR-heated, horizontal flow OMVPE reactor on N^+ GaAs substrates oriented at 6° off (100) towards $\langle 111 \rangle A$. The $In_{0.3}Ga_{0.7}As_{0.997}N_{0.003}/GaAs$ QWs were grown at $535^\circ C$ using trimethylindium, trimethylgallium, 100% arsine, and dimethylhydrazine (DMHy). Diethyltellurium and carbon tetrachloride were used as Te-doping and C-doping precursors, respectively. The growth rate of the $In_{0.3}Ga_{0.7}As_{0.995}N_{0.005}$ and GaAs layers were 5.4, and 8 Å/sec, respectively, and the ratio of $[DMHy]/([DMHy]+[AsH_3])$ was fixed at 0.6. To eliminate the Te memory effect [3] that reduced the radiative efficiency of the GaInNAs/GaAs MQWs, in-situ cleaning the quartz reactor and graphite susceptor with hydrogen chloride at $830^\circ C$ were employed prior to the regrowth of the MQW active region and the p-cladding layer.

Pulsed lasing has been achieved at room temperature by edge-emitting GaInNAs/GaAs lasers with 3 QWs (7 nm wells separated by 10 nm barriers), $Al_{0.3}Ga_{0.7}As$ cladding layers, a cavity length of 1000 μm and a stripe width W that varies from 2 μm to 60 μm . The light-vs-current characteristic and lasing spectrum of a device with $W=60 \mu m$ are shown in fig. 2, with a threshold current of 350 mA and a current density of $\sim 635 A/cm^2$, and a lasing wavelength of $\sim 1.165 \mu m$ at 1.0 A. The temperature dependence of the threshold current for these devices show a characteristic temperature of $T_0 = 125 K - 133 K$. The longest lasing wavelength achieved was $\sim 1200 nm$. The dependence of the lasing characteristics on W has been obtained. Figure 3 shows the characteristics of a laser with $W=25 \mu m$, which was defined by the selective wet oxidation of an $Al_{0.98}Ga_{0.02}As$ layer. The device has a threshold current of 245 mA and a threshold current density of $950 A/cm^2$, with a lasing wavelength of $\sim 1.16 \mu m$.

- [1] M. Kondow, et al., IEEE J. Quantum electronics, Vol. 3, pp.719-730, 1997.
 [2] S. Sato, S. Satoh, Electron. Lett., Vol. 34, no. 15, pp. 1495-1497, 1998.
 [3] N. Y. Li, C. P. Hains, K. Yang, and J. Cheng, submitted to Appl. Phys. Lett., 1999.

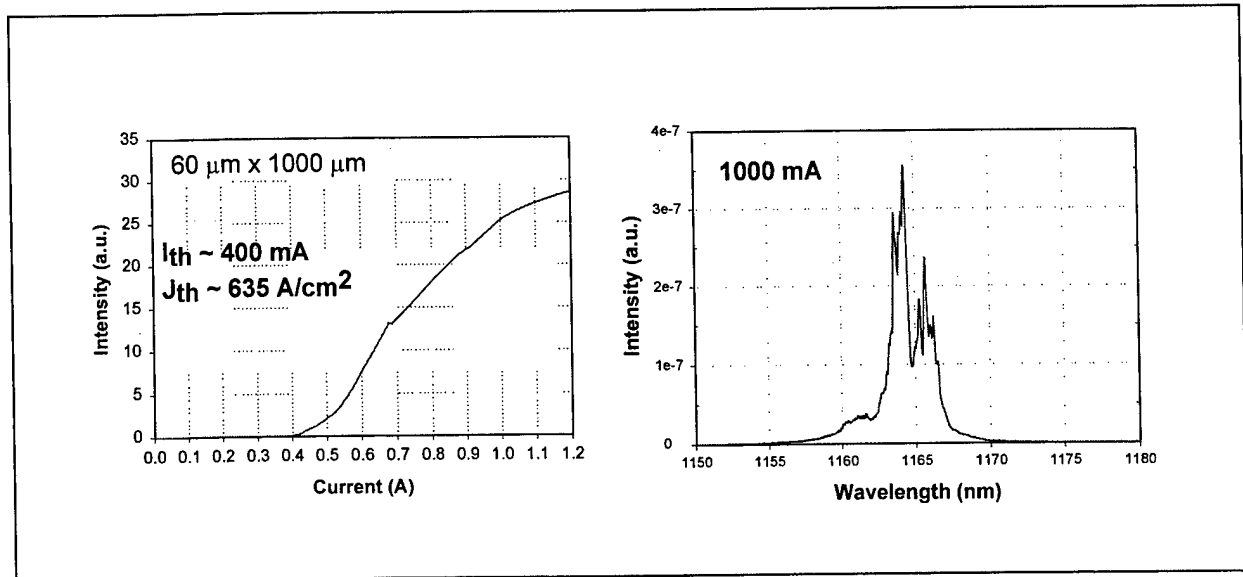


Figure 2. The pulsed lasing characteristic and lasing spectrum of a 3-QW GaInNAs/GaAs laser with $W=60 \mu m$ at 300 K.

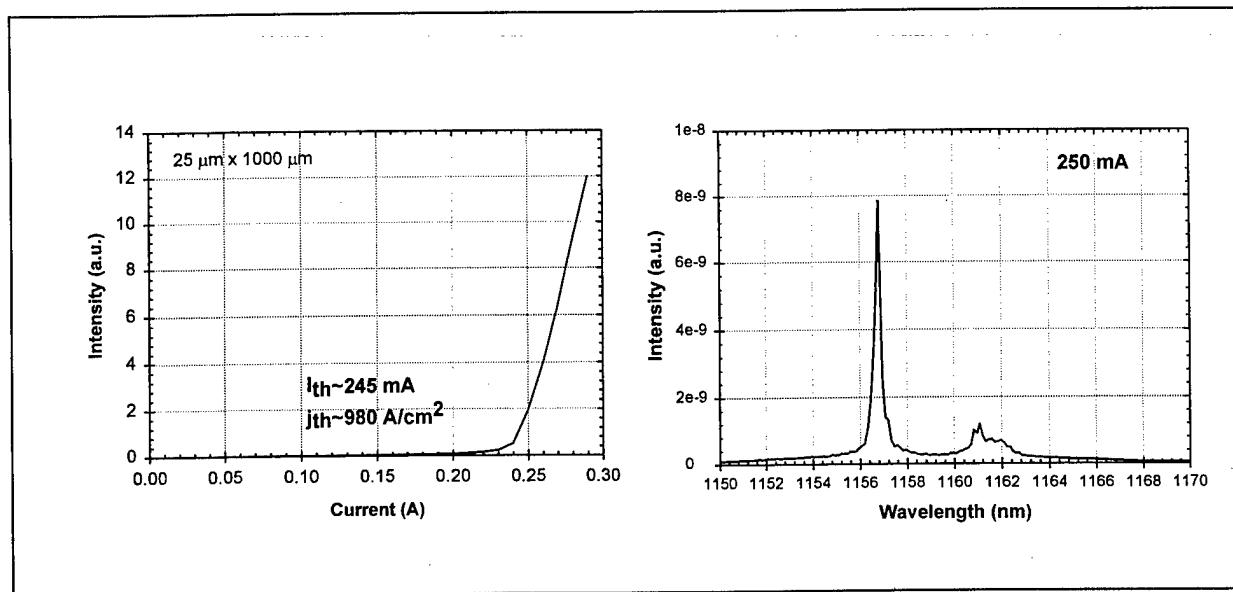


Figure 3. The pulsed light-vs-current characteristic and lasing spectrum of a 3-QW GaInNAs/GaAs laser at 300 K, with $W = 25\ \mu\text{m}$ defined by the selective lateral oxidation of an $\text{Al}_{0.98}\text{Ga}_{0.02}\text{As}$ layer.